



## Comparative Physicochemical Properties of Isolated Pectin from Various Tropical Fruit Peel Wastes

FD Erika Setyajati<sup>1</sup>, Vincentia K Prasetyo<sup>1</sup>, Amelia S Husin<sup>1</sup>, Monica C Ratri<sup>2</sup>, Sendy Junedi<sup>3</sup>, Sanjayadi Sanjayadi<sup>4</sup>, Agustina Setiawati<sup>1\*</sup>

<sup>1</sup>Faculty of Pharmacy, Sanata Dharma University, Sleman, Yogyakarta 55284, Indonesia

<sup>2</sup>Chemistry Education Study Program, Sanata Dharma University, Sleman, Yogyakarta 55284, Indonesia

<sup>3</sup>Faculty of Biotechnology, Universitas Atma Jaya Yogyakarta, Jl Babarsari No. 44, Janti, Caturtunggal, Depok, Sleman, Yogyakarta 55281, Indonesia

<sup>4</sup>Faculty of Pharmacy, School of Medicine and Health Sciences, Atma Jaya Catholic University of Indonesia, Pluit Campus, Jl. Pluit Raya No. 2, Jakarta 14440, Indonesia

### ARTICLE INFO

#### Article history:

Received 31 January 2023

Revised 20 February 2022

Accepted 21 February 2023

Published online 01 March 2023

**Copyright:** © 2023 Setyajati *et al.* This is an open-access article distributed under the terms of the [Creative Commons Attribution License](https://creativecommons.org/licenses/by/4.0/), which permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.

### ABSTRACT

Pectin is widely used as the main polymer in cosmetics, pharmaceuticals, and biomedical applications. The pectin utilization in diverse fields can contribute to fruit waste processing since waste such as fruit peel serves as a pectin source. This study is aimed to analyze the extraction temperature effect on the physicochemical properties of extracted pectin from various tropical fruit peel waste. In this study, we determined the extracted pectin's physicochemical properties from peel wastes of tropical fruits like papaya, lime, lemon, and dragon fruit using 3% citric acid at 65 and 90°C. A higher pectin yield resulted from a higher extraction temperature of 90°C (8.78 to 27.03 %) than that obtained at 65°C (5.78 to 17.71 %). The spectra of Fourier transform infrared (FT-IR) mainly showed the degradation of pectin, specifically in the cases of papaya, lime, and lemon, indicated by the higher OH peak intensity. All samples extracted were high methoxyl pectin (HM), with degrees of esterification (DE) ranging from 56.98 to 89.63%. Among the fruit peels studied, only the lemon peel pectin extracted at 90°C, with anhydrouronic acid (AUA) content of 77.35%, meets the criteria for food additives and pharmaceutical purposes.

**Keywords:** Pectin, degree of esterification, FT-IR, AUA, fruit peels

### Introduction

Pectin is a carbohydrate polymer, a complex heteropolysaccharide that plays several important functions in the cell wall and exists in higher plants in the cell wall and middle lamella.<sup>1</sup> Galacturonic acid units comprise about 70% of the pectin composition.<sup>2</sup> Rhamnose, galactose, arabinose, glucose, xylose, mannose, and fucose are other monosaccharides in pectin.<sup>3</sup> The backbone of pectin comprises D-galacturonic acid units, connected via  $\alpha$ -1,4-glycosidic linkages or modifying units of residues  $\alpha$ -1,4-linked d-galacturonic acid and  $\alpha$ -1,2-linked l-rhamnose.<sup>4,5</sup> Pectin classification is commonly defined by the degree of esterification (DE) and is expressed as the percentage of methyl-esterified carboxyl groups to the total number of galacturonic acid units ratio. High methoxyl (HM) pectin is defined as pectin with DE higher than 50%; on the other hand, pectin with DE less than 50% is known as low methoxyl (LM) pectin.<sup>2</sup> The high variability of pectin polysaccharides determines the pectin properties in any pectin application.<sup>1</sup>

Pectin is utterly used in the food industry, especially in producing jams, marmalades, jellies, and fruit juices as gelling agents, thickeners, stabilizers, and coatings owing to its gelling properties.<sup>1,6</sup> It is widely considered the main polymer used in cosmetics, pharmaceuticals, biomedical, and tissue engineering applications because of its gelling and thickening capabilities.<sup>3</sup>

\*Corresponding author. E mail: [nina@usd.ac.id](mailto:nina@usd.ac.id)  
Tel: +62-(274)-883037

**Citation:** Setyajati FDE, Prasetyo VK, Husin AS, Ratri MC, Junedi S, Sanjayadi S, Setiawati A. Comparative Physicochemical Properties of Isolated Pectin from Various Tropical Fruit Peel Wastes. *Leaves Extracts. Trop J Nat Prod Res.* 2023; 7(2):2408-2413 <http://www.doi.org/10.26538/tjnpr/v7i2.17>

Official Journal of Natural Product Research Group, Faculty of Pharmacy, University of Benin, Benin City, Nigeria.

In tissue engineering applications, pectin acts as a scaffold in which cells are reseeded to form functional tissues. The gelation mechanisms and properties, different for HM and LM pectins, are affected by intrinsic and extrinsic factors such as DE, charge distribution in the polymer, molecular weight, temperature, pH, ionic strength, and the presence of co-solutes. HM pectins require specific gelation conditions, like an acidic pH solution (pH 2.5 to 3.5) and a minimum quantity of soluble carbohydrate, specifically sucrose (55 to 75%), or other similar co-solutes, such as polyethylene glycol and sorbitol. In contrast, LM pectins have easily gelled in the presence of divalent cations, commonly  $\text{Ca}^{2+}$ .<sup>7</sup> Depending on the DE value, pectins may have various applications. Therefore, determining the characteristics of pectin is crucial for its food, biomedical, and tissue engineering applications.

The production of pectin started in the 1920s to process waste from juice industries.<sup>2</sup> A significant amount of the inedible part of the fruit peel, generated by fruit processing steps, is a good source of pectin.<sup>8</sup> It exists in the cell wall as a protopectin that is insoluble in water. Acid hydrolysis at high temperatures breaks the bonds between the side-chain sugars and cell walls. Subsequently, pectin is released and water-soluble.<sup>3</sup> The application of organic acids, for instance, citric acid, has been reported as an option extraction method for obtaining pectin from clementine peel,<sup>9</sup> apple peel,<sup>10</sup> cocoa husks,<sup>11</sup> sweet lemon peel,<sup>12</sup> sugar beet pulp,<sup>13</sup> passion fruit by-products,<sup>14</sup> and grape pomace.<sup>15</sup> Citric acid is effective for pectin extraction resulting in improved physicochemical properties,<sup>6,10</sup> including preferable pectin color.<sup>16</sup>

In this study, this work extracted pectin from various tropical fruit peels, such as papaya (*Carica papaya* Linn.), lime [*Citrus aurantiifolia* (Christm.) Swingle], dragon fruit [*Hylocereus polyrhizus* (Weber)] and lemon (*Citrus limon* Linn.), at different temperatures: 65°C and 90°C using citric acid (pH 3). Previous studies have reported that pectin yield increased with increasing temperature. However, it decreased when pectin started to hydrolyse.<sup>17,18</sup> Yanilka and colleagues found that the extraction temperature affected the DE values but did not affect the yield and viscosity of the pectin extracted from mango peel.<sup>19</sup> However,

another study revealed that the greatest influential factor for pectin yield was the pH, while time affected the DE values.<sup>14</sup> Thus, the temperature effect on the pectin, physicochemical characteristics, including DE and viscosity properties, has not yet been well-studied.

Hence, this study investigated the temperature extractions' effect on the physicochemical properties of pectin extracted from papaya, lemon, lime, and dragon fruit peels. Our study presented that a higher pectin yield has resulted at the temperature of 90 °C (8.78 to 27.03%) than that obtained at 65 °C (5.78 to 17.71%); the Fourier transform infrared (FT-IR) spectra mainly showed the degradation of pectin, specifically for papaya and lime, indicated by the higher OH peak intensity.

## Materials and Methods

### Materials

Papayas were obtained from Borobudur (Central Java, Indonesia), lemons were collected from Sukoharjo, Central Java. Lime was obtained from a local farm in Sleman (Yogyakarta, Indonesia), and dragon fruits were harvested from Banyuwangi (East Java, Indonesia). All the fruits were harvested and collected in May 2022. The fruits sample were identified in the Herbal Medicine Garden Laboratory, Faculty of Pharmacy, Sanata Dharma University. The collected fruit was cleaned and washed, then saved in a jar with alcohol as a wet herbarium in the Pharmacognosy Phytochemistry Laboratory, Faculty of Pharmacy, Sanata Dharma University. Standard pectin was purchased from Sigma-Aldrich (P9135). Technical-grade citric acid and 96% ethanol were used to extract pectin from the tropical fruit peel.

### Pectin extraction

The tropical fruits as our samples were harvested and washed; then, the peels were cut into small pieces (< 1 cm) and dried at 65°C in the oven. After completely dried, the peels were powdered by using a blender and then stored in a sealed polyethylene bag till further use. Pectin extraction was done by using the conventional method using an acidic solution and heat.<sup>6,12,19</sup> The powders of the fruit peels (10 g) were mixed with a 1% citric acid solution (1:30). In the water bath, the solutions were heated to the desired temperature (65°C or 90°C) and constantly mixed for 90 mins. The pectin extract solutions were filtered using a 100-mesh nylon filter and then with a cotton cloth to obtain as much filtrate as possible. The as-obtained filtrates were cooled to 25°C, and a solution of 96% ethanol was poured, equivalent to the filtrate quantity, under continuous stirring to create contact between the pectin extract solutions and ethanol. The solutions were left overnight, and the precipitated pectin samples were filtered using a 400-mesh nylon filter. The pectin precipitates were washed with 96% ethanol until the ethanol solution was clear. The pectin samples were left at room temperature until most of the ethanol evaporated, and then they were crushed then dried at the range of 45 to 50 °C in the oven. The pectin yields were calculated using the following formula:

$$\text{yield (\%)} = \frac{\text{weight of dried pectin (g)}}{\text{weight of peel powder (g)}} \times 100$$

### Pectin characterization

#### Equivalent weight

The pectin equivalent weight was determined using the procedure and formula described by Ranganna (1995).<sup>20</sup> 1 mL ethanol was used to moisten pectin powder (0.5 g), and the procedure continued by dissolving the moistened pectin powder in 20 mL carbon dioxide-free water under continuous stirring until complete dissolution of pectin occurred. NaCl (0.2 g) and phenolphthalein were dropped, and the resulting solution was then titrated with 0.1 N NaOH until a persistent light pink color was obtained. The following equation was then used to calculate the equivalent weight:

$$\frac{\text{Equivalent weight (g/mol)} = \frac{\text{weight of sample (g)}}{\text{volume of titre (mL)} \times \text{titre normality}} \times 1000$$

#### Methoxyl content

1 mL of 0.1 N NaOH used as the saponification titre during the determination of DE is equivalent to 3.10 mg of -OCH<sub>3</sub>. The following

formula was used to calculate the percentage of methoxyl groups in pectin samples:<sup>20</sup>

$$\text{Methoxyl content (\%)} = 3.10 \times \frac{V_2}{w} \times 100$$

V<sub>2</sub> = saponification titre (mL)

w = weight of the pectin sample (mg)

#### Anhydrouronic acid (AUA) content

The pectins' AUA content was determined by calculating the titrant volumes from the calculation of equivalent weight and methoxyl content. The formula for calculating the AUA content is as follows:<sup>21</sup>

$$\text{AUA (\%)} = \frac{176 \times 0.1a \times 100}{w \times 1000} + \frac{176 \times 0.1b \times 100}{w \times 1000}$$

where one molecular unit of AUA = 176 g, a = volume of titre obtained from the equivalent weight, b = volume of titre obtained from the methoxyl content, and w = samples' weight (g).

#### Degree of esterification (DE)

With a little modification, the titrimetric method from USP43-NF38 (2020) was used to determine the DE values of the extracted pectin samples. The pectin peel powder (0.1 g) was transferred to a 100 mL flask, then 2 mL ethanol was used to moisten the pectin peel powder, followed by dissolving them in 20 mL carbon dioxide-free water under continuous stirring at 40 °C using a magnetic stirrer until complete dissolution of pectin occurred. NaCl (0.2 g) was added to sharpen titration results. The phenolphthalein (some drops) was added, then 0.1 N NaOH was used to titrate the solution until the color of the solution changed to a faint pink. The color persisted even after vigorous shaking. The volume of NaOH was recorded as the initial titre volume V<sub>1</sub> (mL). Thereafter, 5 mL of 0.25 N NaOH was transferred to the flask, and the mixture was stirred at room temperature for 30 mins continuously. NaOH (5 mL) was added to the flask, followed by titration with 0.1 N NaOH until a persistent faint pink color was obtained. The volume of NaOH was recorded as the saponification titre V<sub>2</sub> (mL). The DE value was determined using the following formula:

$$\text{DE (\%)} = \frac{V_2}{V_1 + V_2} \times 100$$

#### Functional group analysis and DE calculation using FT-IR spectroscopy

For functional group analysis, attenuated total reflectance (ATR) FT-IR spectroscopy was performed using a Shimadzu IR Spirit FT-IR spectrometer; 64 scans (wavenumber range of 600-4000 cm<sup>-1</sup>) were accumulated. The pectin functional groups' signal range was established using the similar setting that was used to record the spectra of pectin in previous studies. The FT-IR data was also used to determine the DE value from the areas of the ester carbonyl (1745–1760 cm<sup>-1</sup>) and free carboxylate groups (1620–1640 cm<sup>-1</sup>). The DE values were calculated and analyzed using Origin 9.0. The equation used for calculating the DE values is as follows:<sup>22,23</sup>

$$\text{DE} = \frac{\text{area of esterified carboxyl}}{\text{area of esterified carboxyl groups} + \text{area of nonesterified carboxyl groups}}$$

#### Viscosity of pectin solution

A Rion VT-04F viscometer with rotor number 3 was used to measure the viscosities of the pectin solutions. The experiment was adapted from a previous study.<sup>9</sup> The fruit peel pectin was converted to 1% (w/v) aqueous solution by adding 2 mM CaCl<sub>2</sub> and then dissolved in deionized water under constant stirring using a magnetic stirrer until complete dissolution of pectin occurred. A standard pectin solution was prepared using the same method as the control. The pectin solutions were kept overnight in a cool room at 4°C prior to the measurement. The viscometer was used to measure the pectin solutions' viscosity, and the viscosity data was reported in dPa·s.


## Results and Discussion

In this study, we extracted pectin from tropical fruits of Indonesia, such as papaya (*Carica papaya*), lime (*Citrus aurantifolia*), lemon (*Citrus limo*), and dragon fruit (*Hylocereus polyrhizus*) peels, which are good sources of pectin.<sup>12,24,35</sup> We adopted a green extraction method using citric acid (at 65 and 90°C) rather than traditional ones involving inorganic acids, such as HCl and HNO<sub>3</sub>. These acids release corrosive effluents into the environment and may leave toxic traces in the final product.<sup>9</sup> The heated acid dissolves pectin and other cell wall pectin components (protopectin), thus increasing pectin yield.<sup>26</sup> Figure 1 shows the schematic of pectin extraction from the various tropical fruit peel wastes and its subsequent purification. The fruits were peeled and dried at 65°C in the oven. The peels of papaya and dragon fruit required a longer drying time than those of the other samples. The dried peels were powdered using a blender prior to extraction. Compared to peel powders of the citrus fruits, which were yellowish white, those of papaya and dragon fruit were orange and pinkish, respectively. The pectin extracts were then precipitated and refined by washing them with ethanol. After drying at the range of 45 to 50°C, the physicochemical properties of the refined pectin, for instance, DE, functional groups, and viscosities, were determined (Figure 1).


The ethanol-precipitated pectin samples of papaya and dragon fruit were reddish-brown, while those of lime and lemon had a yellow-white colour (Figure 2a). This is possibly due to the removal of impurities such as betacyanin, red pigment, anthocyanin, and the total phenolic compounds from the peel extract of pectin.<sup>27,28</sup> The wet pectin from papaya had an orange-cream colour, whereas those from the others had a yellowish-white colour (Figure 2b). The drying temperature for all the pectin samples was in the range of 45 to 50°C, which is considered to be optimum owing to the highest extraction yield obtained.<sup>29,30</sup> After drying, the as-obtained pectin samples were brown (Figure 2c); however, according to the International Pectin Producers Association (2009), pectin is usually light in colour. The brownish colour observed in a previous study was reported to be possibly due to the presence of pigments and polyphenol compounds.<sup>31</sup> Thus, oven-drying has indicated some destructive effects on the extracted pectins' structure.<sup>14</sup>

The yield of extracted pectin with citric acid increased with increasing temperature, and the maximum yield was obtained at 90°C, which was higher than that required to induce pectin hydrolysis. Because the short pectin polymer could not be precipitated in ethanol, it resulted in a lower pectin yield, according to a previous study.<sup>17</sup> This study revealed that the yields of extracted pectin from papaya, lime, lemon, and dragon fruit peels using citric acid at 65°C were  $7.34 \pm 0.09$ ,  $9.62 \pm 0.05$ ,  $5.78 \pm 0.24$ , and  $17.71 \pm 0.67\%$ , respectively, which significantly increased to  $8.78 \pm 0.61$  ( $p < 0.05$ ),  $27.03 \pm 0.63$  ( $p < 0.001$ ),  $12.10 \pm 0.36$  ( $p < 0.001$ ), and  $23.24 \pm 0.76\%$  ( $p < 0.001$ ), respectively, as the extraction temperature was increased to 90°C (Figure 2d). A higher extraction yield of pectin from fruit peel waste resulted from a higher temperature of extraction.<sup>31,11</sup>

Furthermore, the physicochemical properties of the extracted pectin from the different fruit peels were evaluated. Table 1 shows the equivalent weights and methoxyl and AUA contents of standard pectin and pectin extracted from the different fruit peels.

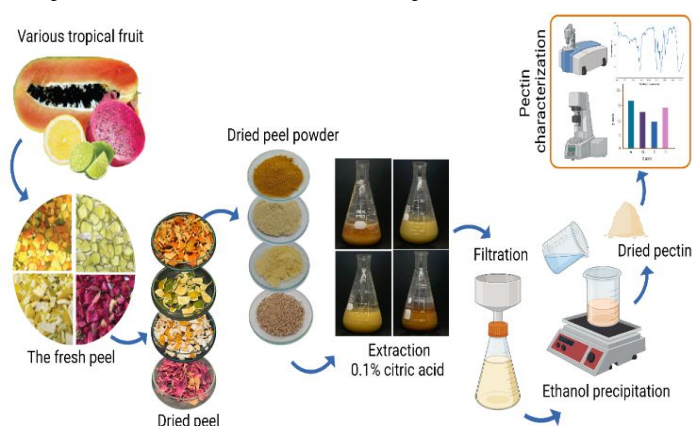

**Figure 1:** Schematic of pectin extraction, purification, and characterization from various tropical fruit peel wastes.

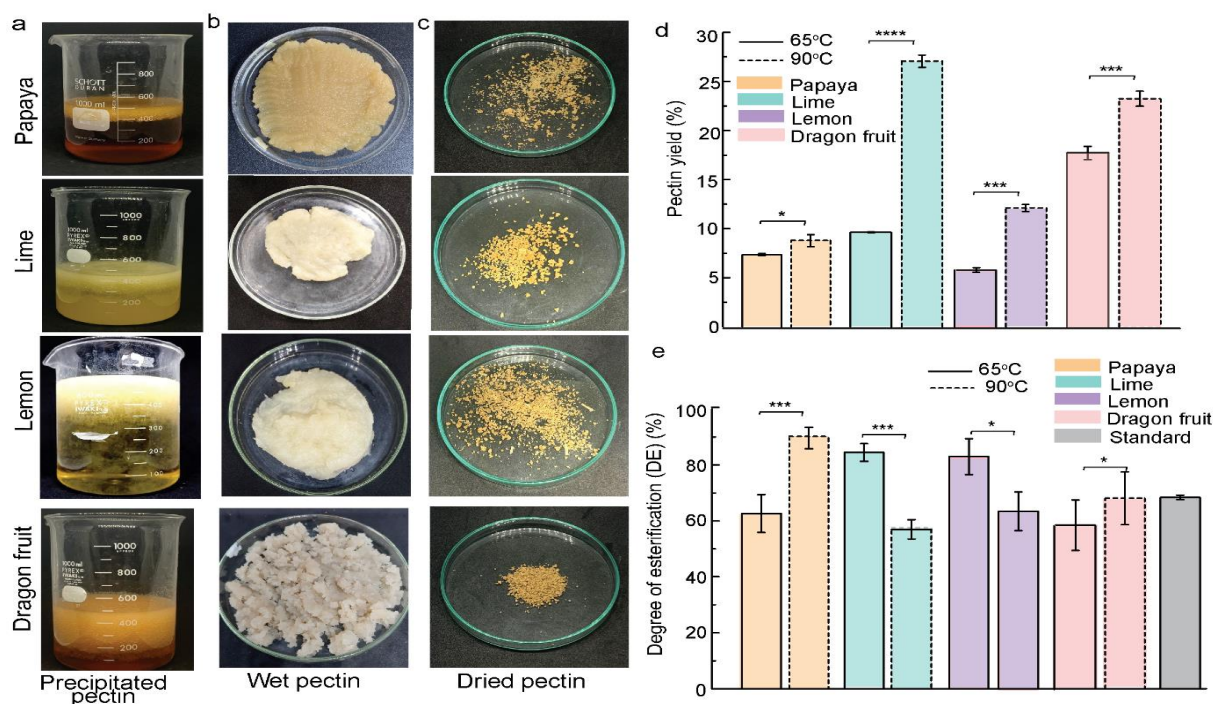

**Figure 2:** Physicochemical properties of refined pectin. a. Ethanol-precipitated pectin; b. Wet pectin; and c. Dried pectin from various fruit peels. d. Yield of isolated pectin obtained from various fruit peels ( $n = 6$ ), e. DE of the isolated pectin at different extraction temperatures ( $n = 4$ ). Statistical significance was determined using one-way ANOVA followed by Tukey's test; \* $p < 0.01$ , and \*\*\* $p < 0.001$ . Error bars indicate mean  $\pm$  standard deviation (S.D.)

The equivalent weights of extracted pectin from papaya, lime, lemon, and dragon fruit peels at 65°C were 1131.75, 1426.71, 1272.12, and 1251.80, respectively, while they were lower for pectin extracted at 90°C, that is, 971.80, 1085.54, 797.5621, and 892.68, respectively. This study also revealed that the pectins' methoxyl content isolated at 90°C was higher than pectin isolated at 65°C for all the samples except those extracted from dragon fruit peel. The proportion of methoxyl group (%) of pectin extracted at 65°C from papaya, lime, lemon, and dragon fruit peels was 4.15, 4.31, 4.37, and 5.64, respectively, while that of pectin extracted at 90°C was 19.30, 8.89, 10.21, and 4.03, respectively. The AUA content of the extracted pectin samples was significantly diverse, from 29.81 to 77.35%. Pectin samples extracted from papaya, lime, lemon, and dragon fruit peels at 65°C showed AUA contents of 29.81%, 32.74%, 56.35%, and 46.23%, respectively, while those of the pectin samples extracted at 90°C were 41.93%, 60.54%, 77.35%, and 43.78%, respectively. The AUA content suggested the purity level of isolated pectin with a minimum recommended value of 65% for pectin applications in the pharmaceutical or food industry. Thus, according to this study, only the lemon peel pectin extracted at 90°C meets the requirements for food additives and pharmaceutical purposes.

DE is an important property that influences pectin application as a scaffold in tissue engineering. To form the porous structure of pectin, it must be cross-linked with a suitable  $\text{Ca}^{2+}$  electrolyte or sugar in low pH solutions.<sup>3,4</sup> In this study, the DE value was determined in two different ways: titrimetric and FT-IR spectral. As determined by the titrimetric method, the pectins' DE values extracted at 65°C from papaya, lime, lemon, and dragon fruit peels were  $62.62 \pm 6.71$ ,  $84.46 \pm 3.16$ ,  $82.99 \pm 6.38$ , and  $58 \pm 9.05$ , respectively (Figure 2e). At a higher temperature of 90°C, the DE values significantly declined to  $56.98 \pm 3.43$  ( $p < 0.001$ ) and  $63.0 \pm 6.90$  ( $p < 0.05$ ) for lime and lemon peel pectin samples, respectively. However, they increased to  $89.63 \pm 3.81$  ( $p < 0.001$ ), and  $68.11 \pm 9.47$  ( $p < 0.05$ ) for papaya and dragon fruit peel pectin samples. The DE value of the standard pectin sample was  $68.40 \pm 0.82$  (Figure 2e).

Further, the FT-IR data was used to determine the DE values. In previous studies, these were determined from the areas of the esterified carbonyl ( $1745\text{--}1760\text{ cm}^{-1}$ ) and free carboxylate groups ( $1620\text{--}1640\text{ cm}^{-1}$ ).<sup>22</sup> The steps of the DE calculation based on the FT-IR data are presented in Supplementary Information. Prior to the measurement of the area under the curve, background subtraction was applied to


normalize the FT-IR peaks (Supplementary 1a). The peaks of the esterified carbonyl and free carboxylate groups were observed at  $1741$  and  $1610\text{ cm}^{-1}$ , respectively (Supplementary 1b). The area under the curve (AUC) was then selected and calculated (Supplementary 1c and 1d). At 65°C, the DE values were 88.38, 83.58, 84.73, and 48.09 for papaya, lime, lemon, and dragon fruit peel pectin samples, respectively, while they decreased to 57.54, 77.32, and 83.36 for pectin extracted from papaya, lime, lemon peels at 90°C. However, the pectin extracted from dragon fruit peel DE value increased to 79.26, whereas that of the standard pectin was 59.21. Overall, all the pectin samples from the various fruit peels were HM pectin. The decrease in the DE values of lime and lemon pectin samples at the higher temperature was possibly due to the hydrolysis of the ester carboxyl. Thus, the possible causes of DE variation are differences in growing environments, plant varieties, and pectin extraction conditions.<sup>32</sup>

A strong band in the range of  $3200\text{--}3600\text{ cm}^{-1}$ , belong to the hydroxyl group (-OH) of the pyranose ring, indicates the specific characteristics of pectin. The bands at approximately  $1730\text{--}1744\text{ cm}^{-1}$  (Figure 3a) and  $1733\text{ cm}^{-1}$  (Figure 3b) were attributed to C=O ester stretching vibration, while the band at approximately  $1600\text{ cm}^{-1}$  was ascribed to the stretching vibration of the methyl ester of the carboxyl group (COO-R). However, COO asymmetric stretching vibrations for pectin samples extracted at 65 and 90°C were observed at  $1400\text{--}1440\text{ cm}^{-1}$  and  $1414\text{--}1460\text{ cm}^{-1}$ , respectively. The carbohydrate fingerprints were investigated in the range of  $950\text{--}1200\text{ cm}^{-1}$ ,<sup>22</sup> as confirmed by the yellow highlighted area in Figures 3a and 3b. The major broad peak at  $3252\text{--}3400\text{ cm}^{-1}$  was indicated to the stretching vibration of the hydroxyl group with intermolecular H-bond of galacturonic acid polymer of all pectin samples extracted at 65 and 90°C (Figure 3a and 3b). A stronger OH band was observed for the papaya, lime, and lemon pectin samples extracted at 90°C than for those extracted at 65°C. The methoxy group of papaya, lime, and lemon pectin samples possibly start to hydrolyze at a higher temperature.


The extraction and application of pectin are influenced by viscosity properties. The higher the molecular weight of pectin means the higher its grade and viscosity.<sup>33</sup> Molecular weight, degree of methylation, concentration, and temperature are factors that influence viscosity.<sup>33,34</sup> A 1% solution of  $\text{Ca}^{2+}$  was used to measure the viscosity. Papaya pectin was darker than any of the other extracted pectin samples (Figure 4a).

**Table 1:** Characteristics of pectin isolated from the various fruit peel wastes

Characteristics	Papaya		Lime		Lemon		Dragon Fruit		Standard
	65°C	90°C	65°C	90°C	65°C	90°C	65°C	90°C	
Weight equivalent (g/mL)	1131.75	971.80	1426.71	1085.54	1272.12	797.5621	1251.80	892.68	892.77
AUA	29.81	41.39	32.74	60.54	56.35	77.35	46.23	43.78	47.17

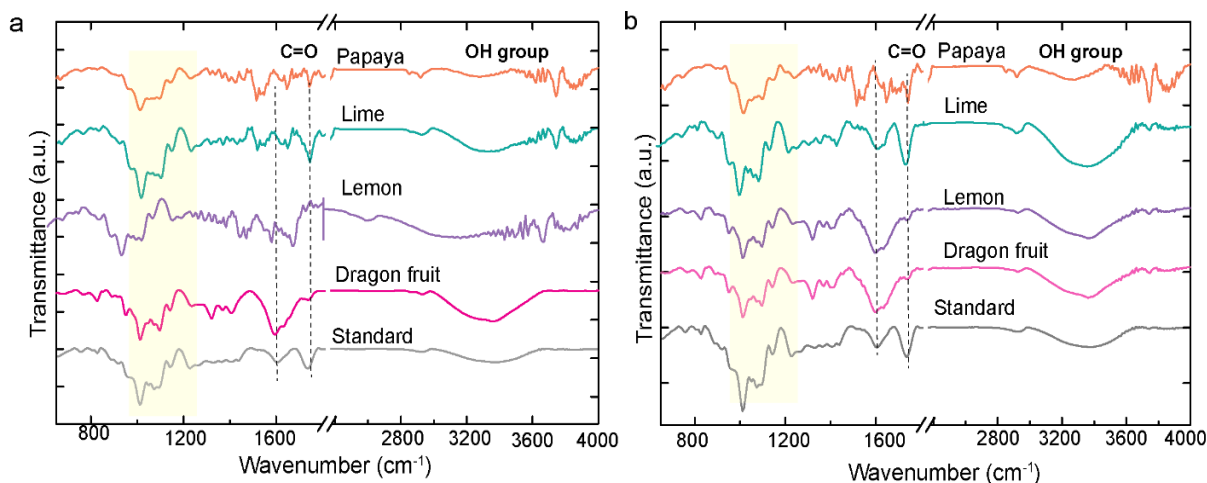

**Figure 3:** FT-IR spectra of pectin samples extracted at: a. 65°C, and b. 90°C.

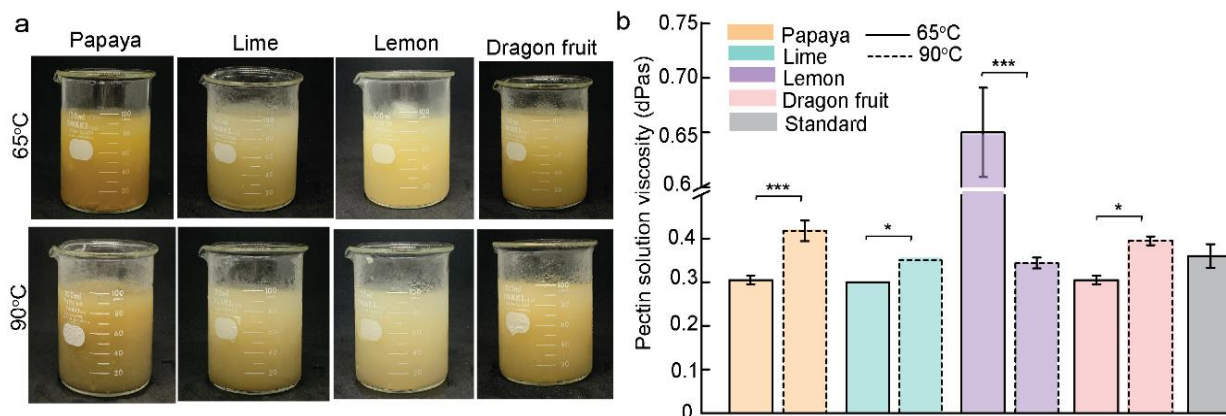

**Figure 4.** Viscosity behaviour of the pectin solutions. a. Appearance of pectin solutions in water containing  $\text{Ca}^{2+}$  b. Viscosity characteristics of pectin extracted at different temperatures ( $n = 3$ ). Statistical significance was determined using a one-way ANOVA followed by Tukey's test; \* $p < 0.05$ , \*\* $p < 0.01$ , and \*\*\* $p < 0.001$ . Error bars indicate means  $\pm$  standard deviation (S.D.)

The viscosities of the pectin solutions were  $0.31 \pm 0.01$ ,  $0.30 \pm 0.00$ ,  $0.65 \pm 0.04$ , and  $0.31 \pm 0.01$  for pectin extracted from papaya, lime, lemon, and dragon fruit peels at  $65^\circ\text{C}$ , while those of the pectin solutions extracted at  $90^\circ\text{C}$  were  $0.42 \pm 0.02$ ,  $0.35 \pm 0.00$ ,  $0.34 \pm 0.01$ , and  $0.39 \pm 0.01$ , respectively (Figure 4b). Most of the pectin solutions exhibited a significant increase in viscosity when extracted at a higher temperature, except that of dragon fruit peel. All the pectin samples were highly methylated pectin however, the viscosities were affected by the divalent ions.

Comprehensively, the pectin samples extracted at a higher temperature from all the tropical fruit peels used in this study exhibited comparable properties with those extracted at a lower temperature. All the extracted pectin samples were categorized as HM pectin, similar to the pectin standard obtained from Citrus peel. The AUA content of lemon peel pectin extracted at  $90^\circ\text{C}$  was 77.35% and met the criteria for food additives and pharmaceutical purposes.

## Conclusion

All the tropical fruit peels used in this study exhibited higher pectin extraction yields at  $90^\circ\text{C}$  than at  $60^\circ\text{C}$ . The pectin extracted from papaya, lime, lemon, and dragon fruit peels were categorized as HM pectins, similar to the standard pectin obtained from Citrus peel. The AUA content of lemon peel pectin extracted at  $90^\circ\text{C}$  (77.35%) meets the criteria for food additives and pharmaceutical purposes.

## Conflict of Interest

The authors declare no conflict of interest.

## Authors' Declaration

The authors hereby declare that the work presented in this article is original and that any liability for claims relating to the content of this article will be borne by them.

## Acknowledgments

The study on the extraction of pectin from dragon fruit peel was supported by the Association of Catholic Higher Learning Institutions (APTİK) under grant No. 008A/JPT.I.2/IV/2022 and the study on pectin extraction from lime peels was supported by the Sanata Dharma University under internal research grant No. 012 Penel/LPPM-USD/II/2023.

## References

- Gawkowska D, Cybulska J, Zdunek A. Structure-related gelling of pectins and linking with other natural compounds:

- A review. *Polymers* (Basel). 2018; 10(7):762.
- Mellinas C, Ramos M, Jiménez A, Garrigós MC. Recent trends in the use of pectin from agro-waste residues as a natural-based biopolymer for food packaging applications. *Materials* (Basel). 2020; 13(3):673.
- Belkheiri A, Forouhar A, Ursu AV, Dubessay P, Pierre G, Delattre C, Djelveh G, Abdelkafi S, Hamdani N, Michaud P. Extraction, characterization, and applications of pectins from plant by-products. *Appl Sci*. 2021; 11(14):6596.
- Kim MS, Chandika P, Jung WK. Recent advances of pectin-based biomedical application: potential of marine pectin. *J Mar Biosci Biotechnol*. 2021; 13(1):28–47.
- de Moura FA, Macagnan FT, Dos Santos LR, Bizzani M, de Oliveira Petkowicz CL, da Silva LP. Characterization and physicochemical properties of pectins extracted from agroindustrial by-products. *J Food Sci Technol*. 2017; 54(10):3111–3117.
- Sandarani M. A review: different extraction techniques of pectin. *J Pharmacogn Nat Prod*. 2017; 3(3):1–5.
- Lara-Espinoza C, Carvajal-Millán E, Balandrán-Quintana R, López-Franco Y, Rascón-Chu A. Pectin and pectin-based composite materials: Beyond food texture. *Molecules*. 2018; 23(4):942.
- Sagar NA, Pareek S, Sharma S, Yahia EM, Lobo MG. Fruit and vegetable waste: bioactive compounds, their extraction, and possible utilization. *Compr Rev Food Sci Food Saf*. 2018; 17(3):512–531.
- He C, Sampers I, Raes K. Isolation of pectin from clementine peel: A new approach based on green extracting agents of citric acid/sodium citrate solutions. *ACS Sustain Chem Eng*. 2021; 9(2):833–843.
- Cho EH, Jung HT, Lee BH, Kim HS, Rhee JK, Yoo SH. Green process development for apple-peel pectin production by organic acid extraction. *Carbohydr Polym*. 2019; 204:97–103.
- Chan SY, Choo WS. Effect of extraction conditions on the yield and chemical properties of pectin from cocoa husks. *Food Chem*. 2013; 141(4):3752–3758.
- Wahengbam E, Nath Shukla R, Kumar A, Anand Mishra A. Extraction of pectin from citrus fruit peel and its utilization in preparation of jelly. *Int J Eng Res Technol*. 2014; 3(5):1925–1932.
- Li DQ, Du GM, Jing WW, Li JF, Yan JY, Liu ZY. Combined effects of independent variables on yield and protein content of pectin extracted from sugar beet pulp by citric acid. *Carbohydr Polym*. 2015; 129(3):108–114.
- Liew SQ, Chin NL, Yusof YA. Extraction and characterization of pectin from passion fruit peels. *Agric Agric Sci Procedia*. 2014; 2(2014):231–236.

15. Rezaei M, Khodaiyan F, Mousavi Z, Hosseini SS, Kazemi M. Optimization of pectin extraction from unripe grape pomace using citric acid and investigation of its physicochemical properties. *Iran J Biosys Eng.* 2021; 51(4):793–804.
16. Leong CM, Noranizan MA, Kharidah M, Choo WS. Physicochemical properties of pectin extracted from jackfruit and chempedak fruit rinds using various acids. *Int Food Res J.* 2016; 23(3):973–978.
17. Hamidon NH, Zaidel DNA. Effect of extraction conditions on pectin yield extracted from sweet potato peels residues using hydrochloric acid. *Chem Eng Trans.* 2017; 56:979–984.
18. Karim R, Uddin MB, Jubayer MF. Optimization of pectin isolation method from pineapple (*Ananas comosus L.*) waste. *Carpathian J Food Sci Technol.* 2014; 6(2):116–122.
19. Ramírez-Benítez JE, Alcantara-Marte YY, Arias Lara GN, Velázquez Vizcaíno ND, Alcantara-Marte YY. Effect of extraction pH and temperature on the physicochemical properties and pectin yield from mango peel (*Mangifera indica L.*). *Agro Product.* 2021.
20. Ranganna S. *Handbook of analysis and quality control for fruits and vegetable products.* (2nd ed). New Delhi: McGraw Hill Publishing; 1995.
21. Khamsocharit P, Laohaphatanalert K, Gavinlertvatana P, Sriroth K, Sangseethong K. Characterization of pectin extracted from banana peels of different varieties. *Food Sci Biotechnol.* 2018; 27(3):623–629.
22. Urias-Orona V, Rascón-Chu A, Lizardi-Mendoza J, Carvajal-Millán E, Gardea AA, Ramírez-Wong B. A novel pectin material: extraction, characterization and gelling properties. *Int J Mol Sci.* 2010; 11(10):3686–3695.
23. Gnanasambandam, R, Proctor A. Determination of pectin degree of esterification by diffuse reflectance. *Food Chem.* 2000; 68(3):327–332.
24. Bhagya Raj GVS, Dash KK. Ultrasound-assisted extraction of phytochemicals from dragon fruit peel: optimization, kinetics and thermodynamic studies. *Ultrason Sonochem.* 2020; 68(3):105180.
25. Demir D, Ceylan S, Göktürk D, Bölgen N. Extraction of pectin from albedo of lemon peels for preparation of tissue engineering scaffolds. *Polym Bull.* 2021; 78(4):2211–2226.
26. Grave LC, McArdle RN, Gohlke JR, Labavitch JM. Impact of heating on carrot firmness: changes in cell wall components. *J Agric Food Chem.* 1994; 42(12):2900–2906.
27. Khoo HE, He X, Tang Y, Li Z, Li C, Zeng Y, Tang J, Sun J. Betacyanins and anthocyanins in pulp and peel of red pitaya (*Hylocereus polyrhizus cv. Jindu*), inhibition of oxidative stress, lipid reducing, and cytotoxic effects. *Front Nutr.* 2022; 9:894438.
28. Shofinita D, Bindar Y, Samadhi TW, Jaelawijaya AA, Fawwaz M. Effect of ethanol addition as extraction solvent on the content of bioactive materials in dragon fruit skin extract and powder. *Reaktor.* 2020; 20(2):68–74.
29. Lin BC, Cze CY. Drying kinetics and optimisation of pectin extraction from banana peels via response surface methodology. *MATEC Web Conf.* 2018; 152(01002).
30. Chua BL, Tang SF, Ali A, Chow YH. Optimisation of pectin production from dragon fruit peels waste: drying, extraction and characterisation studies. *SN Appl Sci.* 2020; 2(4):1–13.
31. Nguyen BMN, Pirak T. Physicochemical properties and antioxidant activities of white dragon fruit peel pectin extracted with conventional and ultrasound-assisted extraction. *Cogent Food Agric.* 2019; 5(1):1633076.
32. Tongkham N, Juntasalay B, Lasunon P, Sengkhamparn N. Dragon fruit peel pectin: microwave-assisted extraction and fuzzy assessment. *Agric Nat Resour.* 2017; 51(4):262–267.
33. Sayah MY, Chabir R, Benyahia H, Kandri YR, Chahdi FO, Touzani H, Errachidi F. Yield, esterification degree and molecular weight evaluation of pectins isolated from orange and grapefruit peels under different conditions. *PLoS One.* 2016; 11(9):e0161751.
34. Kanmani P, Dhivya E, Aravind J, Kumaresan K. Extraction and analysis of pectin from citrus peels: augmenting the yield from citrus limon using statistical experimental design. *Iran J Energy Environ.* 2014; 5(3):303–312.